



10.08.2016

TARDIGRADE ECTX 220

Two Component, Solvent Free, Epoxy Resin Based Top Floor Coating with Orange-Peel Texture

Product Information:

Appearance / Color

Resin – part A : grey, liquid
Hardener – part B : light yellow, liquid

Technical Information

Chemical Structure : Epoxy

Density (ASTM D792 / ISO 1183 / DIN 53479)

Resin – part A : 1.750 kg/l
Hardener – part B : 1.020 kg/l
Mixed resin A + B : 1.650 kg/l

Viscosity (ASTM D2555 / ISO 2555 / DIN EN ISO 2555)


Resin – part A : 28000 mPa·s
Hardener – part B : 450 mPa·s
Mixed resin A + B : 6500 mPa·s


Water Absorption (ASTM D570-98 / ISO 62 / DIN 53495)

0.001

Potlife

63 minutes (23 °C).

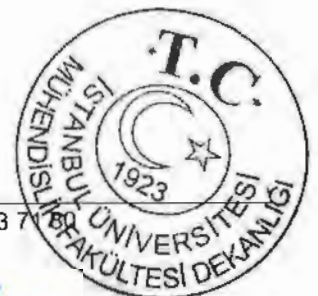


Prof. Dr. Ismail AYDIN
BSc, DIC, PhD



10.08.2016

TARDIGRADE ECTX 220

Two Component, Solvent Free, Epoxy Resin Based Top Floor Coating with Orange-Peel Texture

Mechanical / Physical Properties

TEST	METHOD			VALUE		
				Average	Maximum	Minimum
Compressive strength	ASTM D695	ISO 604	DIN 53454	52 MPa	63 MPa	49 MPa
Flexural strength	ASTM D790	ISO 178	DIN 53452	26.21 MPa	32.64 MPa	21.17 MPa
Maximum force	ASTM D638	ISO 527	DIN 53457	419 N	472 N	408 N
% elongation at break	ASTM D638	ISO 527	DIN 53457	11.28%	27.61%	8.49%
Bond strength	ASTM D7234	ISO 16276	DIN 16276	10.83 MPa	13.35 MPa	9.39 MPa
Shore D hardness	ASTM D2240	ISO 868	DIN 53505	74	82	69

Test results for ECTX 220 Two Component, Solvent Free, Epoxy Resin Based Top Floor Coating with Orange-Peel Texture.





10.08.2016

TARDIGRADE ECTX 220

Two Component, Solvent Free, Epoxy Resin Based Top Floor Coating with Orange-Peel Texture

Chemical Resistance

Chemicals	Values
HYDROCHLORIC ACID 25%	2
HYDROCHLORIC ACID 10%	3
NITRIC ACID 25%	2
NITRIC ACID 10%	3
FORMIC ACID 25%	2
FORMIC ACID 10%	3
ACETIC ACID 25%	3
ACETIC ACID 10%	3
SULPHURIC ACID 25%	3
SULPHURIC ACID 10%	3
LACTIC ACID 25%	3
LACTIC ACID 10%	3
ETHYL ALCOHOL	3
AMMONIA	3
PERCHLOROETHYLENE	3
DIESEL FUEL	3
ACETONE	3
FUEL THINNER	3
HYDRAULIC OIL	3
THINNER	3

Excellent 3 Good 2
Low 1 Not resistant 0

Prof. Dr. İsmail AYDIN
Istanbul University
Engineering Faculty
Chemical Engineering Department

34320 Avcılar/ISTANBUL Tel: +90 212 473 70 70 Fax: +90 212 473 71

